

Reprinted from

PHYSICS JOURNAL
OF THE INDONESIAN PHYSICAL SOCIETY

The Basicity and Acidity of Beta Zeolites after Ion-Exchange with
Alkali Metal Cations: a Physicochemical Characterization

Wong Kah Man, Hadi Nur, Abdul Rahim Yacob and Zainab Ramli, Phys. J. IPS **A7** (2004) 0211

Received: January 28th, 2004 ; Accepted for publication: June 7th, 2004



Published by
THE INDONESIAN PHYSICAL SOCIETY
<http://hfi.fisika.net>

PHYSICS JOURNAL OF THE INDONESIAN PHYSICAL SOCIETY

Journal devoted to Applied Physics (Vol. A), Educational Physics (Vol. B), and Theoretical Physics (Vol. C)

URL : <http://pj.hfi.fisika.net>

Editors

Laksana Tri Handoko (Lembaga Ilmu Pengetahuan Indonesia)

Terry Mart (Universitas Indonesia)

Honorary Editors

Anung Kusnowo (Lembaga Ilmu Pengetahuan Indonesia)

Na Peng Bo (Universitas Indonesia)

Muhamad Barmawi (Institut Teknologi Bandung)

Tjia May On (Institut Teknologi Bandung)

Pramudita Anggraita (Badan Tenaga Atom Nasional Yogyakarta)

Muslim (Universitas Gajah Mada)

Types of paper

The following types of paper are welcome in this journal

1. *Letter* : letter is intended for a rapid publication of important new results. An extended version as the follow-up article can be published as a regular paper. A letter is assumed to be no longer than 4 pages.
2. *Regular* : a regular article contains a comprehensive original work.
3. *Comment* : comment is a short paper that criticizes or corrects a regular paper published previously in this journal. Comment is not allowed to exceed 4 printed pages.
4. *Review* : review article is a comprehensive review of a special topic in physics. Submission of this article is only by an invitation from editors.
5. *Proceedings* : proceedings of carefully selected and reviewed conferences organized by THE INDONESIAN PHYSICAL SOCIETY are published as an integral part of the journal.

Paper Submission

The submitted paper should be written in good English. The paper can be sent in the form of :

1. \LaTeX : this is the most preferred form, since it can accelerate the publication process. Visit the above URL site to find the online submission form and the macro used in this journal.
2. *MS Word* : an MS-Word file can be sent through the online submission form.

Additional relevant information on the submission procedure as well as the instruction manual for writing the paper can be found in the journal site above. The communication thereafter is done through the web.

Referees

All submitted papers are subject to a refereeing process. The editor will choose an appropriate referee for every paper. The author whose paper is rejected by a referee has a right to ask the editor to find another referee as long as he/she can convince the editor that his/her paper has not been objectively refereed. The editor has the right to make a decision on the paper. The journal editor has also the right to reject a paper that clearly does not fulfill scientific criteria.

Reprints

Electronic reprints including covers are available from the journal site for free. The hardcopy version can be ordered from the editorial office. Visit the above web-site or send an e-mail to editorial office for additional information regarding reprints.

THE INDONESIAN PHYSICAL SOCIETY

Chairman : Masno Ginting

Vice Chairman : Pramudita Anggraita

Secretary : Edi Tri Astuti, Maria Margaretha Suliyanti

Treasurer : Diah Intani

Secretariat Office : Dynaplast Tower 1st Floor, Boulevard MH Thamrin #1, LIPPO Karawaci 1100
Tangerang 15811, Banten, Indonesia

Phone : +62 (021) 5461122 / 5461214

Fax : +62 (021) 5461160

URL : <http://hfi.fisika.net>

E-mail : info@hfi.fisika.net

The Basicity and Acidity of Beta Zeolites after Ion-Exchange with Alkali Metal Cations: a Physicochemical Characterization

WONG KAH MAN¹, HADI NUR², ABDUL RAHIM YACOB¹ AND ZAINAB RAMLI¹

¹*Department of Chemistry, Faculty of Science, Universiti Teknologi Malaysia, 81310 UTM Skudai, Johor, Malaysia*

²*Ibnu Sina Institute for Fundamental Science Studies, Universiti Teknologi Malaysia, 81310 UTM Skudai, Johor, Malaysia*

ABSTRACT : The structure, basicity and acidity properties of the alkali metals (*Na*, *K* and *Cs*) exchanged zeolite beta were investigated in this work. Infrared (IR) and X-ray diffraction (XRD) were used for structural characterizations, while Temperature programmed desorption (TPD) of *CO*₂ and *NH*₃ were used for the determination of basicity and acidity, respectively. Results reveal that the framework structure of zeolite beta is retained after the exchange but with a successive decrease in the relative crystallinity after the modification. The acidity of zeolite beta was strongly affected by the crystallinity of the ion-exchanged zeolite beta, in which the acidity has decreased significantly with the decrease in the crystallinity. However, the basicity after the exchange was not very significant in comparison to the acidity. The effect of the crystallinity and the type of alkali metal cations on basicity is also shown.

KEYWORDS : acidity, basicity, zeolite beta, ion-exchange, alkali metal cation

E-MAIL : hadi@kimia.fs.utm.my

Received: January 28th, 2004 ; Accepted for publication: June 7th, 2004

1 INTRODUCTION

The acidity and basicity of zeolites plays an important role in their catalytic and adsorption properties. For instance, heterogeneous acid catalysis by zeolites has been intensively investigated especially in petroleum refinery and cracking process [1]. In addition, the basicity is important in processes that require catalytic acid-base pairs, e.g. alcohol dehydrogenation or selective sorption and separation [2]. Thus, fundamental studies on heterogeneous basic catalysts become necessary in order to achieve the success like those heterogeneous acid catalysts.

Zeolite is reported having base property. The fascinating of basicity in zeolitic materials was reviewed recently by Hattori [2] and Barthoumeuf [3-5]. According to Barthoumeuf, acids and bases are conjugated, where the existence of protons in zeolites has to be associated with that of basic sites. The origin of basicity in zeolite is due to the oxygen atom derived from alumina tetrahedral. Basicity of zeolite can be enhanced by changing the electronegative charge of the framework and or by introduction of basic guest in their structure [2-7].

Studies on base zeolite have usually focused on the faujasites structure due to their high aluminum content. Quite a number of reports reviewed the effectiveness of the base zeolite *X* and *Y* in the base catalyzed reaction [8-10]. However, some other zeolitic materials, which have not yet been investigated with regards to their basicity, might have interesting base structure and character.

Zeolite beta is a high-silica and large pore crystalline aluminosilicate material. The framework structure of zeolite beta possesses three-dimensional 12-membered ring pores with an interconnected channel system [11]. Zeolite beta has high thermal stability and large pore property that desirable for catalyst modification and catalytic activity. It was reported that zeolite beta possess base properties that are greater than expected from its low aluminum chemical composition alone [3, 12]. Nevertheless, only several attempts have been reported in preparing base zeolite beta [12-14]. Here, we study the acidity and basicity of zeolite beta after ion-exchange with alkali metal cations by using Temperature programmed desorption (TPD) of *CO*₂ and *NH*₃, X-ray diffraction (XRD) and Fourier transform infrared (FTIR) in order to corre-

late the acidity and basicity with the structural properties.

2 EXPERIMENTAL

2.1 Preparation

Protonic zeolite beta (*HBeta*) with $SiO_2/Al_2O_3 = 25$ supplied by Zeolyst was used as a starting material in this study. Alkali metal (*Na*, *K*, *Cs*) exchanged zeolite beta were prepared by adding *HBeta* into 1.0 M aqueous solution of the corresponding metal nitrate or acetate at 80 ~ 90°C and stirred overnight. The ratio of zeolite to volume of metal solution that used was 1 : 10 g/ml. It was then filtered and washed with distilled water. This procedure was repeated for six times. Finally, it was dried at 100°C overnight and calcined in air at 500°C for 6 hours with the heating rate of 1°C/min. The exchanged zeolite was labeled as *MBeta*, where M referred to the alkali metals (*Na*, *K* and *Cs*).

2.2 Characterizations

The exchanged zeolites samples were characterized by XRD and IR. The diffractogram was recorded on D500 Siemens Kristalloflex X-ray diffractometer with $CuK\alpha$ as the radiation source with $\lambda = 1.5418$ Å as the radiation source with $\lambda = 1.5418$ Å at 40 kV and 30 mA. Samples were measured in the range of 2θ of 2° to 60° at room temperature with step time of 0.02°/s. The FTIR spectra were recorded at room temperature with 4 cm^{-1} resolutions between 4000 ~ 400 cm^{-1} by using FTIR Perkin Elmer 1600 series. While, the IR spectra of hydroxyl groups for the exchanged zeolite beta were recorded on the FTIR Shimadzu 8000 series. Self-supported wafers (~ 10 mg) were heated at 400°C under vacuum for 2 h. The spectra were then recorded at room temperature in absorbance mode with 2 cm^{-1} resolutions.

The basicity property of the prepared base zeolite beta was characterized by *TPD-CO₂*, acquired using TPD/R/O 1100 ThermoFinnigan. Sample weighing 0.15 ~ 0.25 g was pretreated in a flow of nitrogen at 400°C for 2 h. Sample was then exposed to *CO₂* at a rate of 20 ml/min for 30 min at 40°C. The temperature was raised from 40 ~ 600°C. The desorbed gases were analyzed by TCD. *TPD-NH₃* has also been carried out with the same condition. The samples were pretreated at 450°C and the *NH₃* is adsorbed at 80°C.

3 RESULTS AND DISCUSSION

3.1 Physical properties

The XRD diffraction pattern of the exchanged zeolite beta is shown in Fig. 1. Peaks at 7.8°, 16.5°,

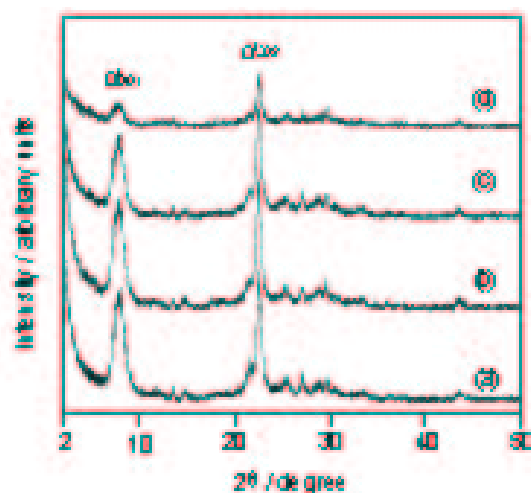


FIGURE 1: X-ray diffraction patterns of the exchanged zeolite beta: (a) *HBeta*, (b) *NaBeta*, (c) *KBeta* and (d) *CsBeta*.

21.4°, 22.5°, 25.3°, 26.9°, 28.8°, 29.5° and 43.5° were observed. Both intense peaks at 7.8° and 22.5° are assigned to the d_{001} and d_{302} respectively, as reported by Perez-Periente et al. [15]. The broad peaks at 7.8° is the characteristic peak for the faulted structure, while the sharp peak at 22.5° is due to the tetragonal and monoclinic symmetry structure of zeolite beta. The presence of all the typical diffractions peaks of zeolite beta (Fig. 1) in each sample indicates the retaining of the framework structure of zeolite beta after ion exchanging with 1.0 M aqueous solution of alkali metal cations, i.e. Na^+ , K^+ and Cs^+ . However, the intensity of the diffraction peaks of the exchanged samples decreases consecutively after the exchanged indicating the deterioration of the crystal structure of zeolite beta has occurred.

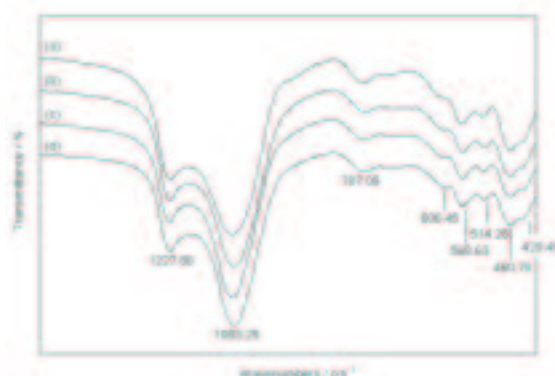


FIGURE 2: IR spectra of the exchanged zeolite beta: (a) *HBeta*, (b) *NaBeta*, (c) *KBeta* and (d) *CsBeta*.

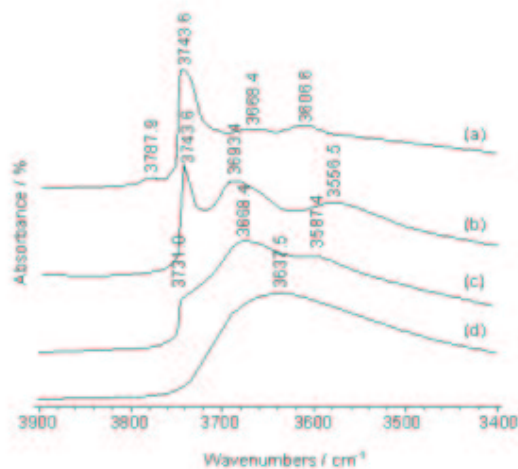


FIGURE 3: IR spectra of the exchanged samples after heated at 400°C for 2 h under vacuum: (a) *HBeta*, (b) *NaBeta*, (c) *KBeta* and (d) *CsBeta*.

The relative crystallinity of the exchanged zeolite beta was tabulated in Table 1. It was calculated based on the intensity of the peak at 22° in comparison with the parent *HBeta*. It is shown that the relative crystallinity of zeolite beta decreases with the increase in size and the electropositive character of alkali metal cations, in the order of $Na^+ < K^+ < Cs^+$. It was suggested that the decreased in the crystallinity might be due to the strong interaction of the cation with the oxygen atom of the alumina tetrahedral in the zeolite framework. As the electropositive characteristic of the cations increased from Na^+ to Cs^+ , the stronger interaction of the cations with the oxygen atoms of the alumina tetrahedra is expected, thus weaken the bond of the oxygen with the rest of zeolite framework. It then explained the decrease of about 60% of the crystallinity of *CsBeta* compared to the parent *HBeta*.

The IR spectra of the exchanged zeolite beta samples are shown in Fig. 2. There are several typical bands that can be observed in the spectrums for all samples. The bands in the region of 1250 ~ 1200 cm^{-1} , 1100 ~ 1050 cm^{-1} and 800 ~ 750 cm^{-1} are assigned to the external asymmetric stretching, internal asymmetric stretching and symmetric stretching of TO_4 ($T = Si, Al$) respectively. The double 6-membered ring and double 4-membered ring vibrations that can be observed respectively at 570 ~ 560 cm^{-1} and 520 ~ 510 cm^{-1} indicate the framework structure of zeolite. Meanwhile, band at around 462 cm^{-1} is assigned to the $T-O$ bending. This result is in an agreement to the XRD findings, where it shows the retaining of the structure after the exchanged.

Fig. 3 shows the IR spectra of the dehydrated ex-

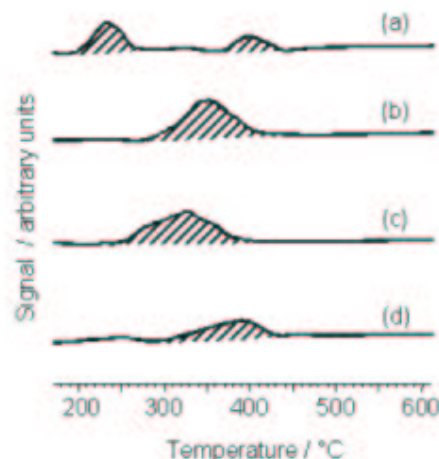


FIGURE 4: $TPD-CO_2$ thermograms of the exchanged zeolite beta: (a) *HBeta*, (b) *NaBeta*, (c) *KBeta* and (d) *CsBeta*.

changed zeolite samples at the OH stretching region. Bands that appeared in the samples are *Si(OH)-Al* groups in the framework (3606.6 cm^{-1}), and the hydroxyl group that bonded with the extraframework aluminium (3668.4 cm^{-1}). A small band near 3780 cm^{-1} is only observed in parent *HBeta*. This band is assigned to the isolated extra-framework $AlOOH^+$ species. The vibration band at 3743 cm^{-1} is assigned to the $O-H$ stretching of silanol group [16-18]. The intensity of this band however decreases with the increase of the size of the cations exchanged. This suggests that besides the ion-exchange process which occurred at the oxygen vicinity of the alumina tetrahedral framework, some of the alkaline metals might have exchanged with the silanol defect sites and occluded at this sites, causing the decrease in the intensity of the silanol group.

Cs^+ has the largest size compare to Na^+ and K^+ and most of the cations shows predominantly to occupy the defect sites rather than the normal ion-exchanged process of the narrow channels from the zeolite framework. This explained the missing band of the OH silanol group in *Cs-Beta* sample.

3.2 Basicity and acidity

Basicity and acidity properties were characterized by Temperature programmed desorption (TPD) to measure the number and strength of base and acid sites that available on the surface of a catalyst. A mild acidic CO_2 was used as probe for basicity and NH_3 for acidity. The strength and amount of base sites are reflected in the desorption temperature and the peak area, respectively, in a TPD plot.

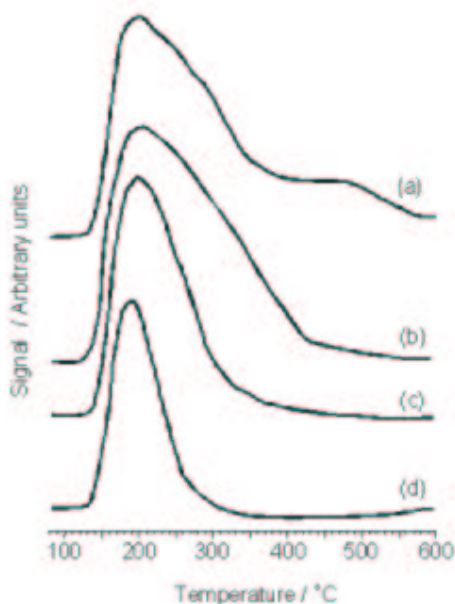


FIGURE 5: $TPD-NH_3$ thermograms of the exchanged zeolite beta: (a) $HBeta$, (b) $NaBeta$, (c) $KBeta$ and (d) $CsBeta$.

The $TPD-CO_2$ thermograms of the exchanged zeolite beta is as shown in Fig. 4. One expects that by exchanging the protons with alkali metal with a lower electronegativity, the oxygen charge will increase and thus increase the basicity of the zeolite. However, the results show no increment of the basic strength in zeolite beta after exchange with sodium, potassium and cesium compared to the parent H-Beta. As shown in Fig. 4, the broad peaks at $240^\circ C$ and $390^\circ C$ for $HBeta$, $350^\circ C$ for $NaBeta$, $330^\circ C$ for $KBeta$ and $390^\circ C$ for $CsBeta$ were observed. It reveals that the trend of the basic strength of $HBeta$, $NaBeta$, $KBeta$ and $CsBeta$ does not follow the trend of the size and the electropositive character of alkali metal cations ($Na^+ < K^+ < Cs^+$). The basic strength also does not follow the trend of the relative crystallinity (see Tab. 1). $CsBeta$ is supposed to create the highest the basic strength. However, it shows that its basic strength is similar to those the parent $H-Beta$.

Tab. 1 gives the number of base sites counted from $TPD-CO_2$. From TPD results it was observed that the amount of base sites among the samples was different. Compared to $HBeta$, the concentration of base sites in $NaBeta$ and $KBeta$ is significantly higher. It also reveals that the concentration of base sites in $CsBeta$ and $HBeta$ are about the same. Theoretically, the basicity must be affected by the strength and the amount of the base sites. In order to show

that the base strength and the amount of the base sites affect the basicity, the Sanderson electronegativity equivalence method (SEEM) [19] is adapted. The SEEM can determine the negative charge carried by the oxygen in zeolite frameworks. The intermediate electronegativity S_{int} of a given material reflects the mean electronegativity reached by all the atoms as a result of electron transfer during formation of the compound. For a compound $P_p Q_q R_r$, the intermediate electronegativity S_{int} is given by,

$$S_{int} = \left(S_P^p S_Q^q S_R^r \right)^{1/p+q+r}, \quad (1)$$

where the composition of the catalyst is $P_p Q_q R_r \dots$, S is the elemental electronegativity, and S_{int} is the intermediate electronegativity. The electronegativity gives access to the negative partial charge on the oxygen atom in the framework by,

$$\delta_0 = \frac{S_{int} - S_0}{2.08 \sqrt{S_0}}. \quad (2)$$

The oxygen charge of the ion-exchanged zeolite beta that calculated based on SEEM are tabulated in Tab. 1. As shown in Tab. 1, it is found that the basicity of the $HBeta$, $NaBeta$ and $KBeta$ is correlated with their oxygen charge. Thus, the basicity of zeolite beta is depending on the amount of sodium and potassium that has been exchanged in the zeolite beta framework. On contrary, cesium exchanged zeolite beta has lower basicity even though the calculated oxygen charge is the highest among all the samples. This might due to the cesium cations are located at the silanol defect sites which is corresponded to the peak around 3740 cm^{-1} in Fig. 3 [16]. This argument is supported by the fact that the silanol defect sites band in the IR hydroxyl group study is disappear (Fig. 3). Since the base strength is also dependent on the structure, it should be noted that the basicity is also affected by the crystallinity of the $CsBeta$. One considers that the lower the crystallinity, the higher is the amount of the silanol defect sites. It confirms that if the crystallinity is taking into account, as shown in Tab. 1, the value of the oxygen charge ($-\delta_0$ times relative crystallinity) which is related to the basicity is become low. Therefore, the low basicity that due to the occupancy of cesium at defect site in $CsBeta$ is correlated with the oxygen charge.

The acidity was also measured with TPD by using NH_3 as probe. The $TPD-NH_3$ thermograms that obtained are as shown in Fig. 5. The acidity of zeolite beta decrease significantly after exchanging with alkali metal cations in the order of $H^+ > Na^+ > K^+ > Cs^+$. By exchanging the proton in zeolite beta framework with alkali metal cations, the crystallinity of the

- [17] P. J. Kunkeler, B. J. Zuurdeeg, J. C. van der Waal, J. A. van Bokhoven, D. C. Koningsberger and H. van Bekkum, *J. Catal.* **180** (1998) 234.
- [18] D. Prasetyoko, *MSc Thesis, Universiti Teknologi Malaysia* (2001).
- [19] R. T. Sanderson, *Chemical Bonds and Bond Energy*, Academic Press, New York (1983).
- [20] J. A. Rabo, and G. J. Gajda, *Catal. Rev. Sci. Eng.* **31** (1989) 385.